

Return address: P.O. box 337, 7500 AH Enschede, The Netherlands

Superior Manufacturing Group
Att.: Mrs. G. Direkx
Achterzeedijk 57
NL-2992 SB
BARENDRECHT
The Netherlands

Report

Project number : 89204607
Report number : 89204607.02br

Received:

A sample of floor covering a mat, marked as: “**Niru Cushion-Ease Solid FR/ESD DISS, 91x91 cm, black.**”. Received on the 24th of October 2013.
TÜV sample reference: MT13-38576.02.

Identification parameters according to the applicant:

Name	:	661 Cushion Ease Solid™ ESD FR
Sample dimension	:	Mats, 91x91 cm
Type of manufacturing	:	Compression moulding
Type of use surface	:	Uni
Composition/ Used material	:	100% Nitrile Fire Retardant rubber
Total mass per unit area kg/m ²	:	14.5
Total thickness, mm	:	19
Colour	:	Uni, black
Roll number	:	556S0033-4
Production number	:	661S0033BL
Use of fire-retardant	:	Yes, in rubber compound

Sampling procedure:

Samples have been selected and send by the applicant.
The test house has had no influence on the sampling procedure.

Request:

Classification of burning behaviour according to EN 13501-1:2007:A1:2009.

Test method:

Ignitability (direct impingement of flame) : EN ISO 11925-2.
Reaction to fire (radiant panel) : EN ISO 9239-1.

Results and conclusion:

See page two and three.

Appendix:

See page four up to and including eleven.

TÜV Rheinland Nederland B.V.
The Netherlands

Postal address:
P.O. Box 337
7500 AH Enschede

Parking and delivery:
Josink Esweg 10
7545 PN Enschede

www.tuv.com/nl

T +31 88 888 7888
F +31 88 888 7859

Ilse.pierik@nl.tuv.com

Date

November 12th, 2013

Project number
89204607

Report number
89204607.02br

Phone number client
+31 180 643 115

Fax number client
+31 180 611 551

Article

Niru Cush-Ease Sol ESD/ FR

Appendix

I : Flooring Radiant Panel Single
Specimen Report – 8 pages

TRN applies General Terms & Conditions
which are filed at the office of the Clerk for
civil affairs at the Court in Zutphen (the
Netherlands) under number 35/2010,
dated November 17th 2010.

CONCLUSION

According to EN 13501-1:2007+ A1:2009 the tested sample of the aforementioned quality **661 Cushion Ease Solid™ ESD FR** in relation to its reaction to fire behaviour is classified: **B_{fl}**.

The additional classification in relation to smoke production is: **s1**.

The aforementioned quality meets the requirement of reaction to fire classification:
B_{fl} – s1

Date
November 12th, 2013

Project number
89204607

Report number
89204607.02br

Article
Niru Cush-Ease Sol ESD/ FR

Page
3/11

The classification is valid for the following end use applications:

- End use substrates of classes A1 and A2-s1,d0 , for example fibre cement board.
- Loose laid or by any means of fixation.

Statements:

The test results only relate to the behaviour of the test specimens of the examined product under the particular conditions of the test in laboratory conditions; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use. The method might not be suitable if the product is exposed to much larger flames or heat radiant sources.

The validity of this report will expire five years after its issue or directly after alterations or modifications of the examined product (combination)(s) and/or the criteria. This report shall not be reproduced, except in full, without the written approval of the testing laboratory.

This document does not represent type approval or certification of the product

Author:
Mrs. I. Pierik

Review and approval:
Mr. J. Brinks

All rights reserved.

No part of this report may be reproduced, provided to and/or examined by third parties, and/or published by print, photoprint, microfilm, in electronic form or any other means without the explicit previous written consent of TÜV Rheinland Nederland B.V.

The results are based upon the samples received and have not to be representative for the total production. Besides TÜV Rheinland Nederland B.V. had no influence on the sampling.

In case this report was drafted within the context of an assignment to TÜV Rheinland Nederland B.V., the rights and obligations of contracting parties are subject to the General Terms & Conditions for Advisory, Research and Certification assignments to TÜV Rheinland Nederland B.V. and/or the relevant agreement concluded between the contracting parties.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Project number
89204607

Report produced with the Fire Testing Technology FRPSoft software

page 1

Report number
89204607.02br

Flooring Radiant Panel Single Specimen Report

Article
Niru Cush-Ease Sol ESD/ FR

Standard : EN ISO 9239-1:2002
 Laboratory : TÜV Rheinland Nederland B.V.
 Sponsor : SMG 89204607
 Date of test : Nov. 05 2013

Page
4/11

Specimen description : MT13-38576.02 Solid ESD Cushion Ease
 Test name : Prod #1
 File name : D:\FRPFILES\13110009.CSV
 Test number in series : 4

Flux calibration file name : C:\FRPSOFT\CALIB\FLX13009.CSV

Thickness (mm) :
 Density (kg/m³) :

Test duration : 25 minutes 10 seconds (1510 s)
 Substrate used? : Yes
 Substrate : none
 Fixing method : none
 Conditioned? : Yes
 Conditioning temp. (°C) : 23
 Conditioning RH (%) : 50

Test Results

Time to ignition : 2 minutes 02 seconds (122 s)
 Time to flameout : 25 minutes 04 seconds (1504 s)
 Extent of burning (mm) : 210
 Critical flux at extinguishment (kW/m²) : 9.19
 HF-10 (kW/m²) : 9.49
 HF-20 (kW/m²) : 9.19
 HF-30 (kW/m²) : >= 10.9
 Flame spread at 10 minutes (mm) : 190
 Flame spread at 20 minutes (mm) : 210
 Flame spread at 30 minutes (mm) : -1
 Peak light attenuation (%) : 31.39
 Time to peak light attenuation : 17 minutes 33 seconds (1053 s)
 Total integrated smoke (%.min) : 382.16
Potential classification : A2(II)/B(f)
Smoke production classification : s1

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Project number
89204607


Report number
89204607.02br

Article
Niru Cush-Ease Sol ESD/ FR

Page
5/11

Report produced with the Fire Testing Technology FRPSoft software

page 2

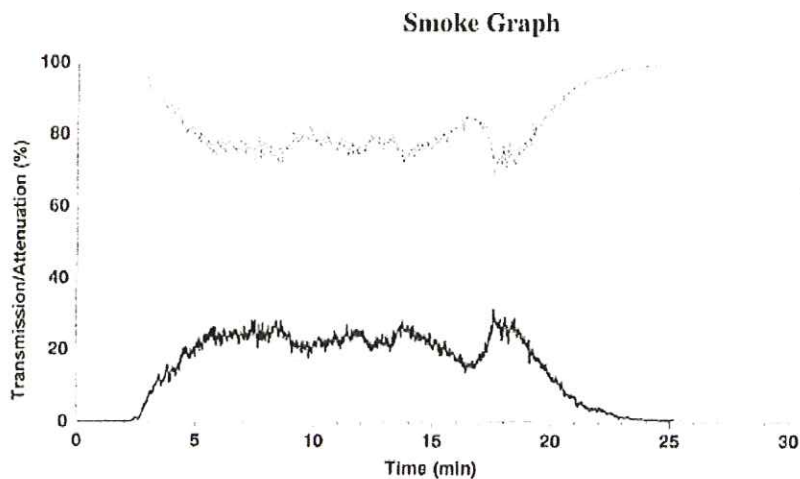

Test name : Prod #1
File name : D:\FRPFILES\13110009.CSV

Rake Results

Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)	Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)
60	248	11.3	2.620	510	-	3.6	-
110	371	10.6	3.686	560	-	3.0	-
160	505	9.9	4.639	610	-	2.5	-
210	728	9.2	5.943	660	-	2.1	-
260	-	8.2	-	710	-	1.8	-
310	-	7.2	-	760	-	1.5	-
360	-	6.2	-	810	-	1.4	-
410	-	5.2	-	860	-	1.2	-
460	-	4.3	-	910	-	1.1	-

Comments

Specimen extinguished naturally.

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Project number
89204607

Report number
89204607.02br

Article
Niru Cush-Ease Sol ESD/ FR

Page
6/11

Report produced with the Fire Testing Technology FRPSoft software

Page 1

Flooring Radiant Panel Single Specimen Report

Standard : EN ISO 9239-1:2002
Laboratory : TÜV Rheinland Nederland B.V.
Sponsor : SMG 89204607
Date of test : Nov. 05 2013

Specimen description : MT 13-38576.02 Solid ESD Cushion Base
Test name : Prod/ Cross #2
File name : D:\FRPFJLES\13110010.CSV
Test number in series : 4

Flux calibration file name : C:\FRPSOFT\CALIB\FLX13009.CSV

Thickness (mm) :
Density (kg/m³) :

Test duration : 23 minutes 46 seconds (1426 s)
Substrate used? : Yes
Substrate : none
Fixing method : none
Conditioned? : Yes
Conditioning temp. (°C) : 23
Conditioning RH (%) : 50

Test Results

Time to ignition : 2 minutes 02 seconds (122 s)
Time to flameout : 23 minutes 43 seconds (1423 s)
Extent of burning (mm) : 180
Critical flux at extinguishment (kW/m²) : 9.64
HF-10 (kW/m²) : 9.64
HF-20 (kW/m²) : 9.64
HF-30 (kW/m²) : >= 10.9
Flame spread at 10 minutes (mm) : 180
Flame spread at 20 minutes (mm) : 180
Flame spread at 30 minutes (mm) : -1
Peak light attenuation (%) : 32.06
Time to peak light attenuation : 6 minutes 19 seconds (379 s)
Total integrated smoke (%.min) : 268.36

Potential classification : **A2(II)/B(II)**
Smoke production classification : **s1**

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the safe criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Project number
89204607


Report number
89204607.02br

Article
Niru Cush-Ease Sol ESD/ FR

Page
7/11

Report produced with the Fire Testing Technology FRPSoft software

page 2

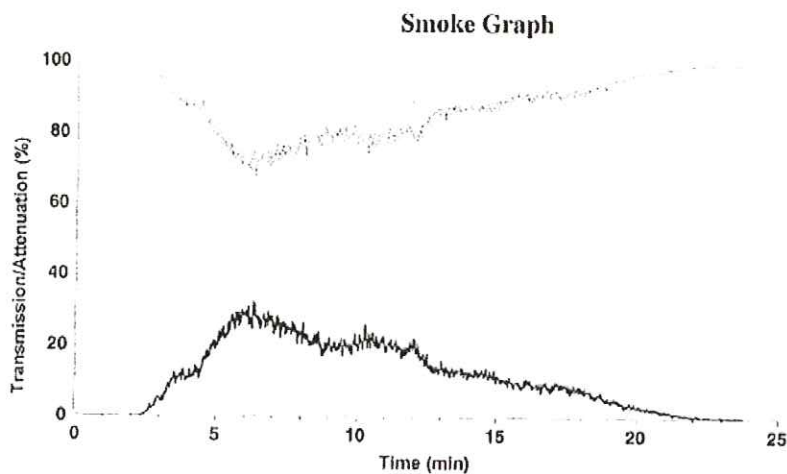

Test name : Prod/ Cross #2
 File name : D:\FRPFILES\13110010.CSV

Rake Results

Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)	Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)
60	252	11.3	2.662	510	-	3.6	-
110	351	10.6	3.487	560	-	3.0	-
160	507	9.9	4.658	610	-	2.5	-
210	-	9.2	-	660	-	2.1	-
260	-	8.2	-	710	-	1.8	-
310	-	7.2	-	760	-	1.5	-
360	-	6.2	-	810	-	1.4	-
410	-	5.2	-	860	-	1.2	-
460	-	4.3	-	910	-	1.1	-

Comments

Specimen extinguished naturally.

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Project number
89204607

Report number
89204607.02br

Report produced with the Fire Testing Technology FRPSOFT software

page 1

Flooring Radiant Panel Single Specimen Report

Article
Niru Cush-Ease Sol ESD/ FR

Standard : EN ISO 9239-1:2002
Laboratory : TÜV Rheinland Nederland B.V.
Sponsor : SMG 89204607
Date of test : Nov. 05 2013

Page
8/11

Specimen description : MT13-38576.02 Solid ESD Cushion Ease
Test name : Prod/Cross #3
File name : D:\FRPFILES\13110011.CSV
Test number in series : 4

Flux calibration file name : C:\FRPSOFT\CALIB\FLX13009.CSV

Thickness (mm) :
Density (kg/m³) :

Test duration : 24 minutes 18 seconds (1458 s)
Substrate used? : Yes
Substrate : none
Fixing method : none
Conditioned? : Yes
Conditioning temp. (°C) : 23
Conditioning RH (%) : 50

Test Results

Time to ignition : 2 minutes 02 seconds (122 s)
Time to flameout : 24 minutes 15 seconds (1455 s)
Extent of burning (mm) : 230
Critical flux at extinguishment (kW/m²) : 8.78
HF-10 (kW/m²) : 9.19
HF-20 (kW/m²) : 8.78
HF-30 (kW/m²) : >= 10.9
Flame spread at 10 minutes (mm) : 210
Flame spread at 20 minutes (mm) : 230
Flame spread at 30 minutes (mm) : -1
Peak light attenuation (%) : 28.26
Time to peak light attenuation : 10 minutes 05 seconds (605 s)
Total integrated smoke (%.min) : 267.83
Potential classification : A2(H)/B(f)
Smoke production classification : s1

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Project number
89204607


Report number
89204607.02br

Article
Niru Cush-Ease Sol ESD/ FR

Page
9/11

Report produced with the Fire Testing Technology FRPSoft software

Page 2

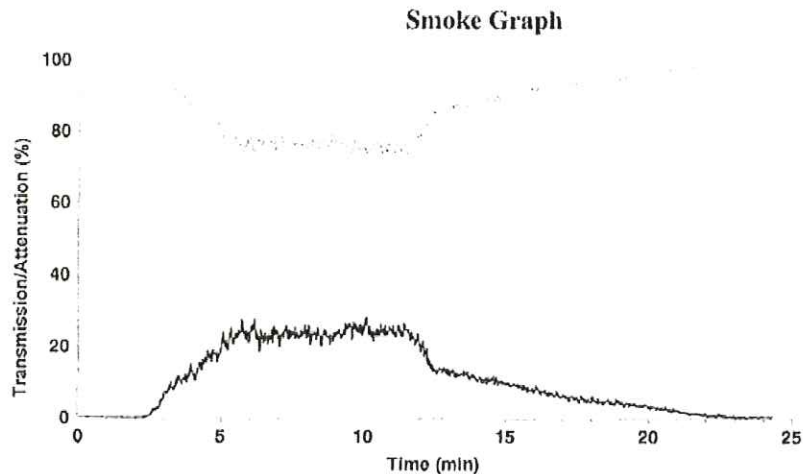

Test name : Prod/Cross #3
File name : D:\FRPFILES\13110011.CSV

Rake Results

Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)	Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)
60	248	11.3	2,620	510	-	3.6	-
110	354	10.6	3,517	560	-	3.0	-
160	475	9.9	4,364	610	-	2.5	-
210	588	9.2	4,800	660	-	2.1	-
260	-	8.2	-	710	-	1.8	-
310	-	7.2	-	760	-	1.5	-
360	-	6.2	-	810	-	1.4	-
410	-	5.2	-	860	-	1.2	-
460	-	4.3	-	910	-	1.1	-

Comments

Specimen extinguished naturally.

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Date
November 12th, 2013

Report produced with the Fire Testing Technology FRPSoft software

page 1

Project number
89204607

Report number
89204607.02br

Flooring Radiant Panel Single Specimen Report

Article
Niru Cush-Ease Sol ESD/ FR

Page
10/11

Standard : EN ISO 9239-1:2002
Laboratory : TÜV Rheinland Nederland B.V.
Sponsor : SMG 89204607
Date of test : Nov. 05 2013

Specimen description : MT13-38576.02 Solid ESD Cushion Ease
Test name : Prod/Cross # 4
File name : D:\FRPFILES\13110012.CSV
Test number in series : 4

Flux calibration file name : CAERPSOFT\CALIBWFLX13009.CSV

Thickness (mm) :
Density (kg/m³) :

Test duration : 23 minutes 56 seconds (1436 s)
Substrate used? : Yes
Substrate : none
Fixing method : none
Conditioned? : Yes
Conditioning temp. (°C) : 23
Conditioning RH (%) : 50

Test Results

Time to ignition : 2 minutes 01 seconds (121 s)
Time to flameout : 23 minutes 54 seconds (1434 s)
Extent of burning (mm) : 170
Critical flux at extinguishment (kW/m²) : 9.79
HF-10 (kW/m²) : 10.06
HF-20 (kW/m²) : 9.79
HF-30 (kW/m²) : >= 10.9
Flame spread at 10 minutes (mm) : 150
Flame spread at 20 minutes (mm) : 170
Flame spread at 30 minutes (mm) : -1
Peak light attenuation (%) : 28.36
Time to peak light attenuation : 6 minutes 23 seconds (383 s)
Total integrated smoke (%.min) : 241.57

Potential classification : A2(f)/B(f)
Smoke production classification : s1

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test, they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

APPENDIX I: Flooring Radiant Panel Single Specimen Report

Report produced with the Fire Testing Technology FRPSoft software

page 2


Date
November 12th, 2013

Project number
89204607

Report number
89204607.02br

Article
Niru Cush-Ease Sol ESD/ FR

Page
11/11

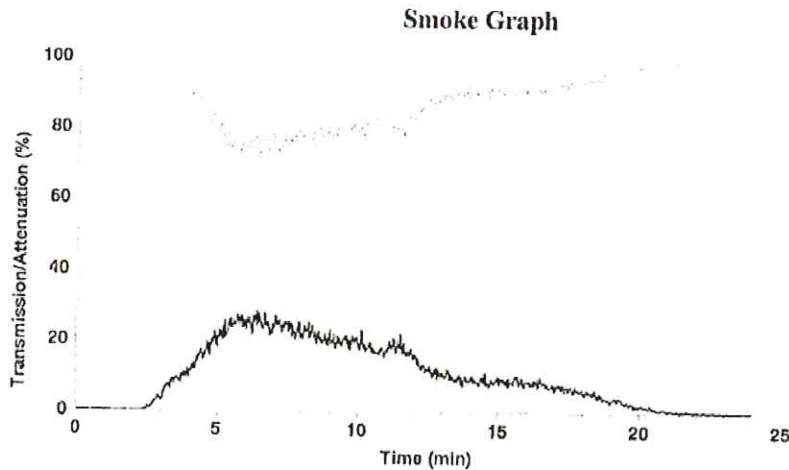

Test name : Prod/Cross # 4
 File name : D:\FRPFILES\13110012.CSV

Rake Results

Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)	Position (mm)	Time (s)	Flux (kW/m ²)	Qsb (MJ/m ²)
60	252	11.3	2.662	510	-	3.6	-
110	380	10.6	3.775	560	-	3.0	-
160	619	9.9	5.687	610	-	2.5	-
210	-	9.2	-	660	-	2.1	-
260	-	8.2	-	710	-	1.8	-
310	-	7.2	-	760	-	1.5	-
360	-	6.2	-	810	-	1.4	-
410	-	5.2	-	860	-	1.2	-
460	-	4.3	-	910	-	1.1	-

Comments

Specimen extinguished naturally.

These results relate only to the behaviour of the specimens of the product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.